

HETEROCYCLES, Vol. 97, No. 2, 2018, pp. 1313 - 1318. © 2018 The Japan Institute of Heterocyclic Chemistry
Received, 26th March, 2018, Accepted, 6th June, 2018, Published online, 8th June, 2018
DOI: 10.3987/COM-18-S(T)92

POLYMORPHISM OF MACROCYCLIC OLIGOTHIOPHENE 8-MERS

Hideyuki Shimizu,^a Tahmina Haque,^a Masataka Takashika,^b Hiroyuki Otani,^b and Masahiko Iyoda^{a*}

^aDepartment of Chemistry, Graduate School of Science and Engineering, Tokyo Metropolitan University, Hachioji, Tokyo 192-0397, Japan. ^bGraduate School of Environment and Information Sciences, Yokohama National University, Hodogaya-ku, Yokohama 240-8501, Japan. E-mail: iyoda@tmu.ac.jp

Dedicated to Professor Kiyoshi Tomioka on the occasion of his 70th birthday

Abstract – Macrocyclic oligothiophene 8-mer *E,E*-**8T6A** composed of eight thienylene, six ethynylene, and two vinylene units exhibits unique polymorphism. In the solid state, *E,E*-**8T6A** formed nanostructured polymorphs such as single crystals, fibers, long and short rods, and square tubes depending on the solvent used for crystallization. In contrast, *E*-**8T7A** with one vinylene unit and **8T8A** without vinylene unit afforded single crystals, microcrystalline, and short rods in the solid state. Morphological difference between *E,E*-**8T6A** and *E*-**8T7A**/**8T8A** is due to the flexibility of the macroring of *E,E*-**8T6A** with two vinylene units, and the shape-persistent but rather flexible *E,E*-**8T6A** forms various polymorphs in the solid state.

Polymorphism is an important concept in chemistry,¹ medicine,² molecular biology,³ and materials science.⁴ In organic chemistry, polymorphism of molecules is mainly due to various semi-equivalent metastable structures in the solid state. Recently, we reported polymorphism of giant macrocycles composed of thienylene, ethynylene, and vinylene building blocks.⁵ Macrocycles *E,E*-**8T6A**, *E*-**8T7A**, and **8T8A** are regarded as an infinite π -conjugated system with a large inner cavity (Figure 1), and their physical properties are strongly affected by their structures in solution and the solid state.^{6,7} Since macrocyclic thiophenes have both moderate molecular rigidity and mobility,² the nanophase separation between interior and exterior sites in large macrocycles results in the formation of attractive polymorphs based on one-dimensional (1D), two-dimensional (2D), and three-dimensional (3D) supramolecular

nanostructures.⁸ In this paper, we report on polymorphism of shape-persistent macrocyclic oligothiophenes caused by a small conformational flexibility of macrorings.


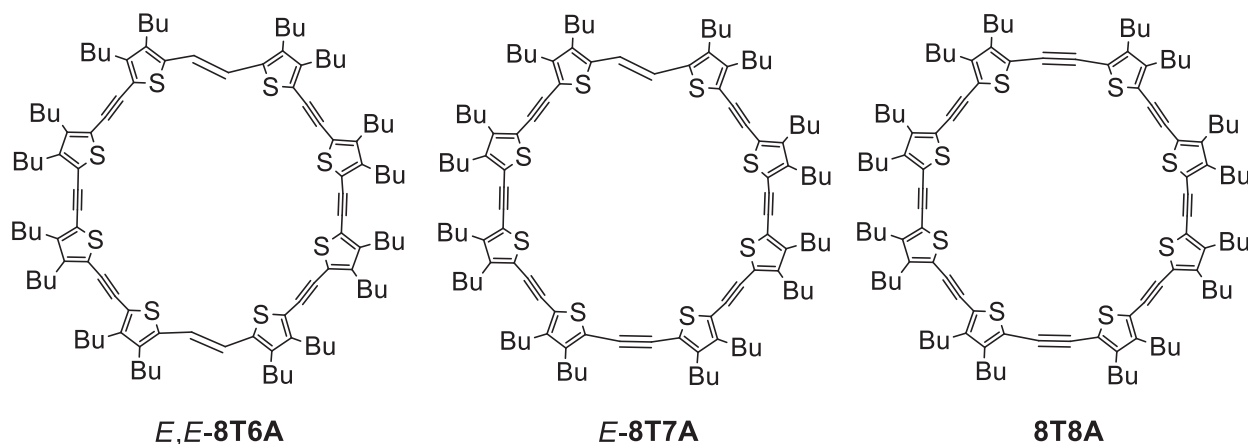


Figure 1. Chemical formulae of macrocyclic oligothiophene 8-mers *E,E*-**8T6A**, *E*-**8T7A**, and **8T8A**

As reported previously, the synthesis of *E,E*-**8T6A** was performed by using a McMurry coupling of the dialdehyde **1** with low-valent titanium reagent (Scheme 1).⁶ *E,E*-**8T6A** was obtained in 35% yield as a main product, together with higher cyclic oligomers.⁶ The synthesis of *E*-**8T7A** was also carried out by a similar McMurry coupling of the dialdehyde **2** to produce *E*-**8T7A** in 47% yield with corresponding higher oligomers.⁷ *E,E*-**8T6A** was converted into **8T8A** by using ‘bromination-dehydrobromination’ procedure in total 21% yield, whereas a similar bromination-dehydrobromination reactions of *E*-**8T7A** resulted in a complex mixture, in which no **8T8A** was included. All macrocyclic oligothiophene 8-mers are stable in the solid state in air at room temperature in spite of the fairly low oxidation potentials (*E,E*-**8T6A**: 0.22 V, *E*-**8T7A**: 0.31 V, and **8T8A**: 0.36 V vs Fc/Fc⁺).

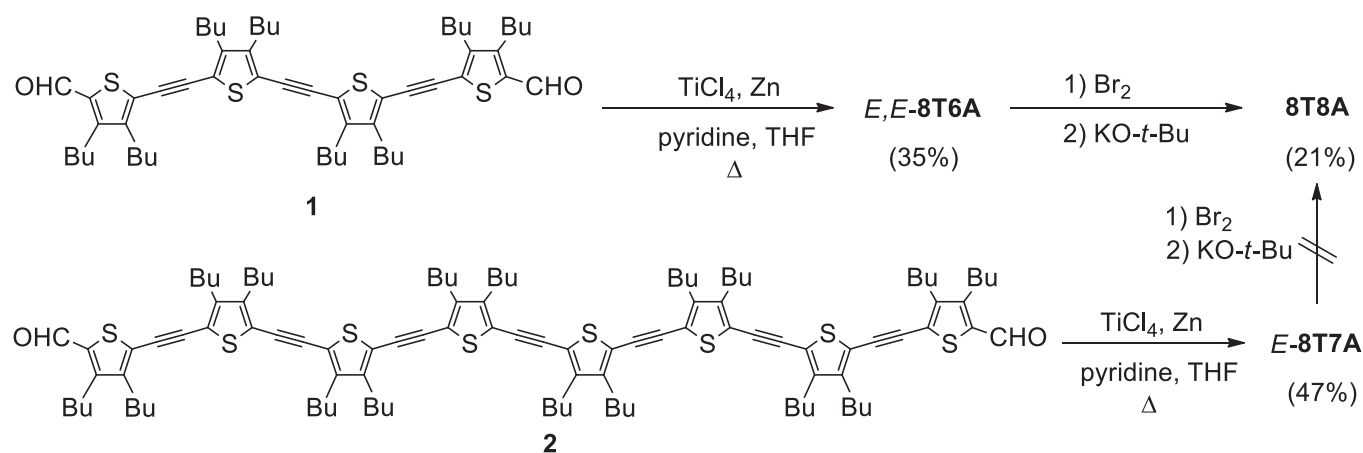

Scheme 1. Synthesis of *E,E*-**8T6A**, *E*-**8T7A**, and **8T8A**

Macrocyclic oligothiophene *E,E*-**8T6A** forms various nanostructures polymorphs depending on solvents used for crystallization (Figure 2). From hot benzene, single crystals of *E,E*-**8T6A** were obtained, whereas a wide variety of fibrous polymorphs precipitated from solution. Thus, fibers, rods, square tubes, and short rods were produced from benzene/hexane, CHCl_3 , benzene/diisopropyl ether (IPE), and toluene, respectively. None of these polymorphs contains any solvent determined by ^1H NMR measurements, but the morphological difference depends on the solvent used.

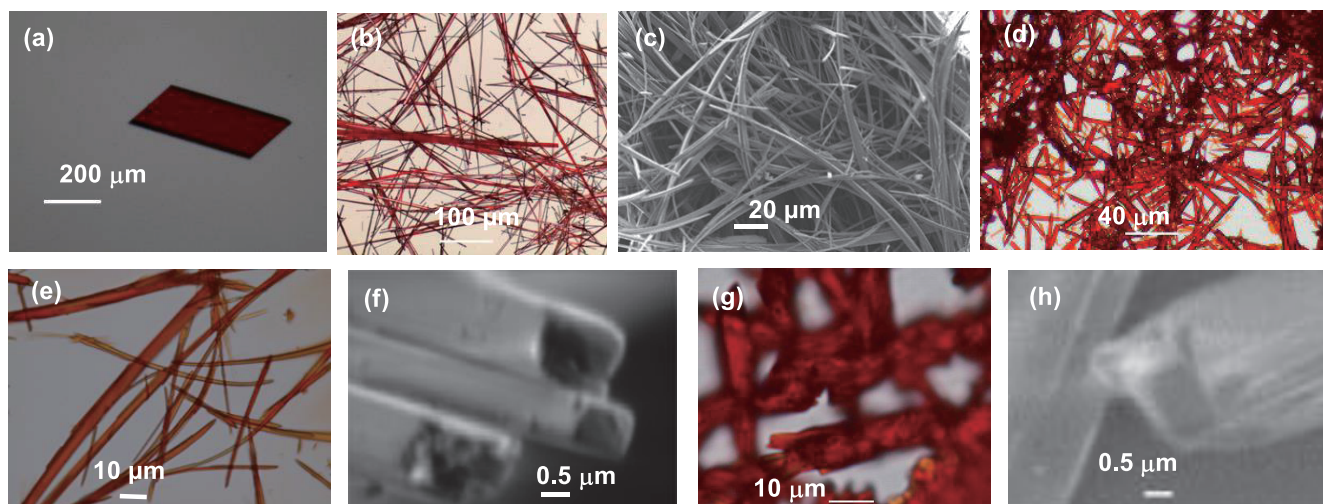


Figure 2. Optical and scanning electron microscopy (SEM) images of nanostructured polymorphs of *E,E*-**8T6A**. Optical images of single crystal from hot benzene (a), fibers from benzene/hexane (b), rods from CHCl_3 (d), square tubes from benzene/IPE (e), and short rods from toluene (g). SEM images of fibers from benzene/hexane (c), square tubes from benzene/IPE (f), and short rods from toluene (h).

As shown in Figure 3a, single crystal of *E,E*-**8T6A** exhibits a typical power pattern of the X-ray diffraction (XRD) profile obtained from the X-ray structural analysis. In contrast, the XRD profile of fibers of *E,E*-**8T6A** shows simple reflections at $2\theta = 3.88^\circ$, 7.76° , and 11.64° corresponding to a lamellar structure (Figure 3b). Since the molecular diameter of *E,E*-**8T6A** is estimated to be 28 \AA , the fibers of *E,E*-**8T6A** have a 1D supramolecular structure stacked in the direction of the fiber. Although the XRD profiles of rods and short rods of *E,E*-**8T6A** exhibit a high crystallinity (Figure 3c),^{ref} reflecting a 3D structure in the crystals, square tubes of *E,E*-**8T6A** have a 1D lamellar structure (Figure 3d). The XRD profile of square tubes of *E,E*-**8T6A** shows simple reflections at $2\theta = 3.77^\circ$, 7.54° , and 11.31° as a 1D structure, and the molecules in the square tubes stack in the direction of the fiber. It is noteworthy that the SEM image of square tubes of *E,E*-**8T6A** indicate an aging of the tube structure under ambient conditions to gradually afford tapes. However, fibers, rods, and short rods of *E,E*-**8T6A** are stable and remain unchanged under ambient conditions.

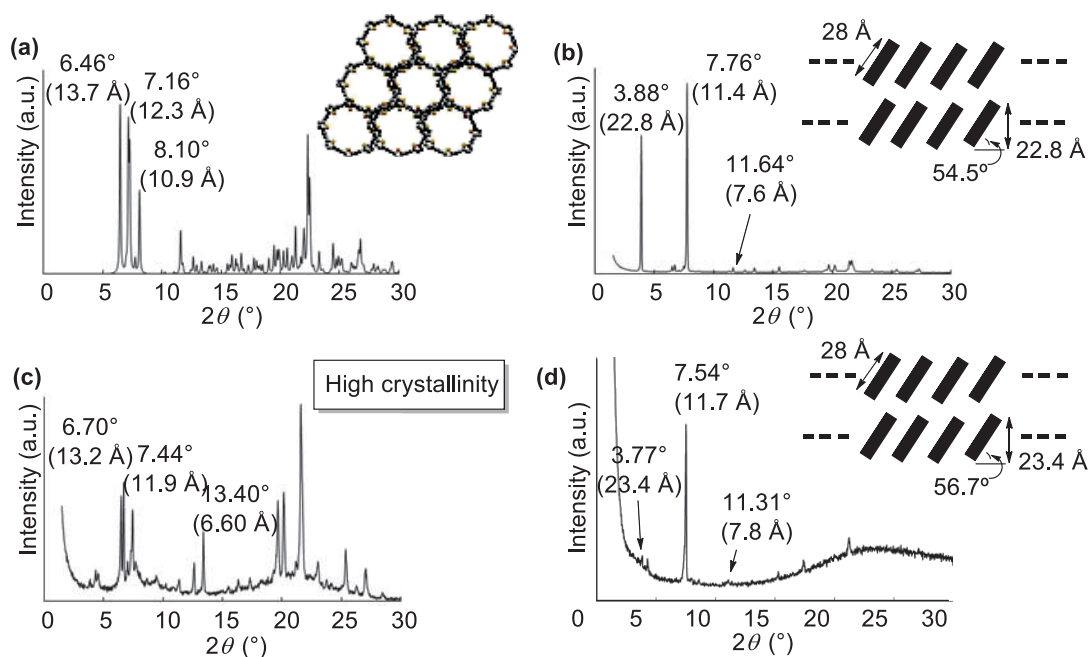


Figure 3. XRD patterns for the single crystal (a), fibers (b), rods (c), and square tubes (d) of *E,E*-**8T6A**

In contrast to the formation of various nanostructured polymorphs of *E,E*-**8T6A**, *E*-**8T7A** affords single crystals from hot benzene and microcrystalline from toluene (Figure 4a). As shown in Figure 4b, microcrystalline of *E*-**8T7A** exhibits low crystallinity different from the XRD profile of single crystals, and the reflections at $2\theta = 21.61^\circ$ and 24.12° can be assigned as a roughly π - π stacked structure. Similarly, **8T8A** produces single crystals from hot benzene, short rods from benzene (Figure 4c), and amorphous film from CS_2 . The XRD profile of short rods of **8T8A** shows rather high 3D crystallinity; however, this profile is different from the XRD profile of single crystals. The difference in the XRD profile between *E,E*-**8T6A** and *E*-**8T7A**/**8T8A** can be explained by the flexibility of macroring, and the shape-persistent but rather flexible *E,E*-**8T6A** forms various polymorphs in the solid state. However, *E*-**8T7A** and **8T8A** have a conformationally rigid macroring, and hence, they afford only limited polymorphs.

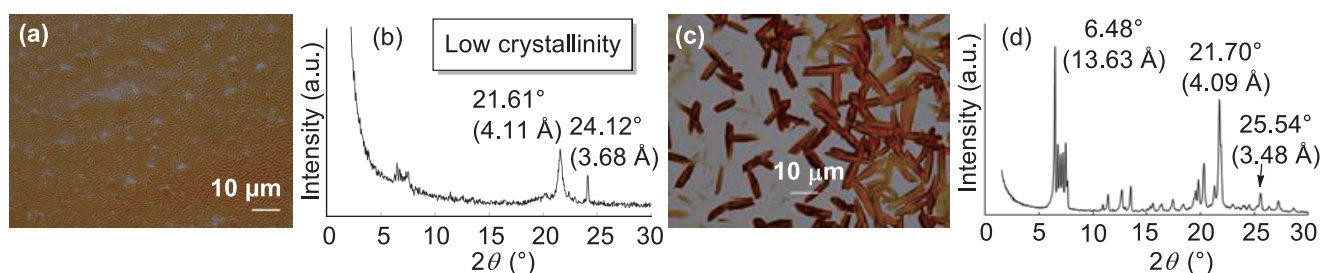


Figure 4. Optical images and XRD profiles of *E*-**8T7A** and **8T8A**. Optical image (a) and XRD profile (b) microcrystalline of *E*-**8T7A**. Optical image (c) and XRD profile (d) of short rods of *E*-**8T6A**.

In summary, polymorphism of macrocyclic oligothiophene 8-mers *E,E*-**8T6A**, *E*-**8T7A**, and **8T8A** is dependent on the nanophase separation between interior and exterior sites in large mobile macrocycles. The shape-persistency and flexibility of macrocycles cause many semi-equivalent metastable structures in the solid state to afford polymorphs, and slightly more flexible *E,E*-**8T6A** compared to *E*-**8T7A**, and **8T8A** produces a variety of polymorphs having attractive structures. Our findings about polymorphism of macrocyclic oligothiophenes open a new guiding principle to design new polymorphs of shape-persistent macrocycles.

EXPERIMENTAL

Synthesis of *E,E*-8T6A**, *E*-**8T7A**, and **8T8A**.** *E,E*-**8T6A**, *E*-**8T7A**, and **8T8A** were prepared according to our reported procedures. *E,E*-**8T6A**, *E*-**8T7A**, and **8T8A** are soluble in benzene, toluene, CH₂Cl₂, CHCl₃, THF, and carbon disulfide; however, these compounds are slightly soluble in hexane, Et₂O, diisopropyl ether (IPE), and EtOAc.

Single crystals of *E,E*-8T6A**, *E*-**8T7A**, and **8T8A** (Figures 2a and 3a).** Single crystals of *E,E*-**8T6A**, *E*-**8T7A**, and **8T8A** were obtained by recrystallization from hot benzene under ambient conditions, and their structures were determined by using X-ray analysis.

Fibers of *E,E*-8T6A** from benzene/hexane (Figures 2b,c and 3b).** In the dark *E,E*-**8T6A** (10 mg) was dissolved in benzene (0.2 mL) and hexane (0.5 mL) at 50 °C. The solution was allowed to stand at room temperature to produce fibers of *E,E*-**8T6A**.

Rods of *E,E*-8T6A** from chloroform (Figures 2d and 3c).** In the dark *E,E*-**8T6A** (10 mg) was dissolved in CHCl₃ (0.2 mL). The solution was cast on a glass plate to produce rods of *E,E*-**8T6A**.

Square tubes of *E,E*-8T6A** from benzene/diisopropyl ether (IPE) (Figures 2e,f and 3d).** In the dark *E,E*-**8T6A** (10 mg) was dissolved in benzene (0.3 mL) and IPE (0.1 mL) at 50 °C. The solution was allowed to stand at room temperature to produce square tubes of *E,E*-**8T6A**.

Short rods of *E,E*-8T6A** from toluene (Figures 2g,h).** In the dark *E,E*-**8T6A** (10 mg) was dissolved in toluene (0.5 mL). The solution was cast on a glass plate to produce short rods of *E,E*-**8T6A**.

Small crystals of *E*-8T7A** from toluene (Figures 4a,c).** *E*-**8T7A** (10 mg) was dissolved in toluene (3.5 mL), and the solution was cast on a glass plate to produce small crystals of *E*-**8T7A**.

Short rods of **8T8A from benzene (Figures 4b,d).** **8T8A** (10 mg) was dissolved in benzene (4 mL), and the solution was cast on a glass plate to produce short rods of *E*-**8T7A**.

ACKNOWLEDGEMENTS

This work was supported by a Grant-in-Aid for Scientific Research from the Ministry of Education, Culture, Sports and Technology, Japan and partly performed under the Cooperative Research Program of

“Network Joint Research Center for Materials and Devices”. We thank Prof. Yoshio Aso and Prof. Masashi Hasegawa for helpful discussions.

REFERENCES AND NOTES

1. Recent reviews: (a) S. Vanghese, M. S. R. N. Kiran, U. Ramamurty, and G. R. Desiraju, *Angew. Chem. Int. Ed.*, 2013, **52**, 2701; (b) A. J. Cruz-Cabeza and J. Bernstein, *Chem. Rev.*, 2014, **114**, 2170; (c) Q. Jiang and M. D. Ward, *Chem. Soc. Rev.*, 2014, **43**, 4965.
2. Books: G. You and M. E. Morris, “Drug Transporters: Molecular Characterization and Role in Drug Disposition: Second Edition”, Wiley Blackwell, 2014.
3. Reviews: (a) A. Grunenberg, J.-O. Henck, and H. W. Siesler, *Int. J. Pharm.*, 1996, **129**, 147; (b) C. Schlötterer, R. Tobler, R. Kofler, and V. Nolte, *Nature Rev. Genetics*, 2014, **15**, 749; (c) F. W. Albert and L. Kruglyak, *Nature Rev. Genetics*, 2015, **16**, 197.
4. Recent reviews: (a) A. J. Cruz-Cabeza, S. M. Reutzel-Edens, and J. Bernstein, *Chem. Soc. Rev.*, 2015, **44**, 8619; (b) G. J. O. Beran, *Chem. Rev.*, 2016, **116**, 5567; (c) T. Hasell and A. I. Cooper, *Nature Rev. Met.*, 2016, **1**, 16053; (d) M. A. White, A. M. Medina-Gonzalez, and J. Vela, *Chem. Eur. J.*, 2018, **24**, 3650.
5. M. Iyoda and H. Shimizu, *Chem. Soc. Rev.*, 2015, **44**, 6411.
6. H. Shimizu, J. D. Cojal González, M. Hasegawa, T. Nishinaga, T. Haque, M. Takase, H. Otani, J. P. Rabe, and M. Iyoda, *J. Am. Chem. Soc.*, 2015, **137**, 3877.
7. H. Shimizu, K. H. Park, H. Otani, S. Aoyagi, T. Nishinaga, Y. Aso, D. Kim, and M. Iyoda, *Chem. Eur. J.*, 2018, **24**, 3793.
8. M. Iyoda, K. Tanaka, H. Shimizu, M. Hasegawa, T. Nishinaga, T. Nishiuchi, Y. Kunugi, T. Ishida, H. Otani, H. Sato, K. Inukai, K. Tahara, and Y. Tobe, *J. Am. Chem. Soc.*, 2014, **136**, 2389.